

PRODUCT TESTING SERVICES

Page:

Date:

1 of 1

09.19.12

O Sojourn Drive Suite 290 💮 🛑 💮 Carrollton, 1

Proj. No White Marble Tile using Marble Grip

Lab: Carrollton, Texas

Client:

Specification: Tested using the BOT-3000 per ASTM C 1028-96 and ANSI B101.1

"Standard Test Method for Determining the Static Coefficient of Friction of Tile and Other Like Surface"

Exposure Time: Two coats for 5 minutes each **Source:** Submitted by SlipDoctors

STATIC COEFFICIENT OF FRICTION (ASTM C 1028-96 and ANSI B101.1)

The coefficient of friction (COF) tests were performed in multiple directions to determine an average COF value of the floor surface when wet. The tests were conducted using distilled water and a Neolite sensor that have been properly maintained to prevent buildup of contaminants, which could affect the COF test results. The results are recorded and documented using the BOT 3000 slip meter.

The COF tests performed are for wet conditions. All of the tests are to be recorded and written report generated. A diagram of the zones are included below. The four measurements were then added for a total and averaged for the Static coefficient of Friction for each substrate.


The ASTM C-1028 / ANSI B-101.1 references wet SCOT using a neolite sensor. No interpretation of the results are provided.




Zone	Description of Area			Test Results		Dangerous			Safe		
A. As Received Untreated							Untreated				
	Test #	South	East	North	West	Average					
	↑	0.47	0.46	0.51	0.47	0.48	0.	44			
	\rightarrow	0.47	0.42	0.42	0.43	0.44					
	\downarrow	0.46	0.44	0.43	0.42	0.44		\downarrow			
	\leftarrow	0.41	0.40	0.42	0.44	0.42				0.0	0.0.4
						0.44	0.1 0.2 0.3 (0.4 0.5 (0.6 0.7	0.8	0.9 1.
B. After Treating for Five (5) minutes with Marble Grip							Dangerous				Safe
	Test #	South	East	North	West	Average	After Treatment				
	↑	0.80	0.72	0.73	0.72	0.74				0.71	
	\rightarrow	0.67	0.68	0.65	0.64	0.66					
	\downarrow	0.67	0.75	0.70	0.67	0.70					
	←	0.78	0.70	0.76	0.68	0.73					
						0.71	0.1 0.2 0.3 0	0.4 0.5 (0.6 0.7	0.8	0.9 1.

Examples of BOT Tests

Before

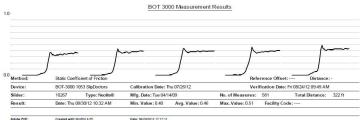

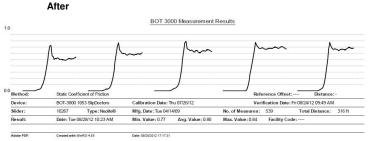

Picture of Surface

Before



After



Testing Services: testing@slindoctors.com

Literature Orders: Literature@slipdoctors.com

Web Site: www.slipdoctors.com